

Conjugated polymer nanocomposites: Synthesis, dielectric, and microwave absorption studies

Anil Ohlan,¹ Kuldeep Singh,¹ Amita Chandra,² V. N. Singh,³ and S. K. Dhawan^{1,a)}

¹*Polymeric and Soft Materials Section, National Physical Laboratory, New Delhi 110012, India*

²*Department of Physics and Astrophysics, University of Delhi, Delhi 110007, India*

³*Department of Physics, Thin Film Laboratory, Indian Institute of Technology Delhi, New Delhi 110016, India*

(Received 2 February 2009; accepted 11 July 2009; published online 21 August 2009)

Nanocomposites of polyaniline with barium ferrite and titanium dioxide (TiO₂) are synthesized via *in situ* emulsion polymerization. The transmission electron microscopy (TEM) and high resolution TEM result shows the formation of array of nanoparticles encapsulated within the polymer chains during the synthesis process. The high value of microwave absorption, 58 dB (>99.999% attenuation) results from the combined effect of the nanoparticles and the polymer matrix. The amount of barium ferrite has the profound effect on permittivity (ϵ), permeability (μ), and microwave absorption of the nanocomposite. The contribution to the absorption value comes mainly due the magnetic losses (μ'') in barium ferrite and dielectric losses (ϵ'') in TiO₂ and polyaniline.

© 2009 American Institute of Physics. [DOI: 10.1063/1.3200958]

I. INTRODUCTION


An unwanted disturbance called electromagnetic interference (EMI) is one that affects an electrical circuit due to electromagnetic (EM) radiation emitted from an external source carrying rapidly changing electrical currents.^{1,2} The disturbance may interrupt, or otherwise degrade or limit the effective performance of the circuit. Intrinsic conducting polymers (ICPs) having extended π -conjugated system with conductivity in semiconductor regime has emerged as a potential class of materials for EMI shielding and microwave absorbers.³⁻⁶ To protect the electronic equipment for the commercial applications, the material with shielding effectiveness (SE) measured in decibel (dB) greater than 30 dB should be adequate, while for military application, the requirements are significantly higher, in the range between 80 and 100 dB. Here we have shown that nanocomposites of polyaniline with barium ferrite and titanium dioxide (TiO₂) named PBT composite possesses the high value of microwave absorption, 58 dB (\sim 99.9999% attenuation). While recently, ICP composites with ferrite, singlewalled carbon nanotube (CNT), and multiwalled CNT have been reported as EMI shielding material with SE of \sim 30 dB having high thickness.⁷⁻⁹ The higher SE of PBT results from the combined effect of the nanoparticles and the polymer matrix. The contribution to the microwave absorption comes mainly from the magnetic losses in barium ferrite and dielectric losses in TiO₂ and polyaniline. The achievement of higher SE can lead them to be used as an additive in paints which acts as coating material and may replace the ferrite/metal coatings. Many research groups are working on this aspect of conjugated polymers, as unlike metals, they not only reflect the EM radiation but also absorb them.¹⁰ The microwave absorbing properties are determined by the complex relative per-

mittivity ($\epsilon_r = \epsilon' - j\epsilon''$), permeability ($\mu_r = \mu' - j\mu''$) and the microstructure of the absorber. Technical requirement for the absorber limits the number of ferromagnetic materials that can be used in the microwave range above few gigahertz.¹¹ However, nanosized ferromagnetic particles have properties that can be varied with the size¹² and are different from those of the bulk materials. At high frequency, the permeability of the magnetic material decreases due to the eddy current losses developed by the EM wave. Therefore, it is better to use conducting matrix to suppress the eddy current phenomenon to enhance the effective interaction with the absorber.¹³ Among the EM wave absorbers, the composites of magnetic particles in the insulating matrix have been extensively studied. Che *et al.*¹⁴ reported the synthesis of CNT encapsulated with Fe nanoparticles showing good absorption behavior but the complex synthesis of CNT filled with magnetic nanoparticles is not favorable for practical applications. Abbas *et al.*¹⁵ reported that the microwave absorption properties of barium hexaferrite and its polymer composite show good attenuation value of 30 dB in the X-band but the synthesis process is mainly governed by mixing the ferrite with the polymer. Moreover, thick samples are required for higher attenuation.

II. EXPERIMENTAL

The synthesis of barium ferrite has been carried out via precursor route¹⁶ by dissolving 1:12:13 molar ratio of barium nitrate, ferric nitrate, and citric acid, respectively, in distilled water. The barium ferrite and TiO₂ were further grinded for 6 h using Retsch "PM-400" planetary-ball mill in tungsten carbide jars. The formation of barium ferrite and TiO₂ phase has been confirmed by x-ray diffractometer. The resulting nanosized barium ferrite along with TiO₂ nanoparticles have been homogenized in 0.3M aqueous solution of dodecyl benzene sulfonic acid (DBSA) to form a whitish brown emulsion solution. Appropriate amount of aniline (0.1M) has been

^{a)}Tel.: +91-11-45609401. FAX: +91-11-25726938. Electronic mail: skdhawan@mail.nplindia.ernet.in.

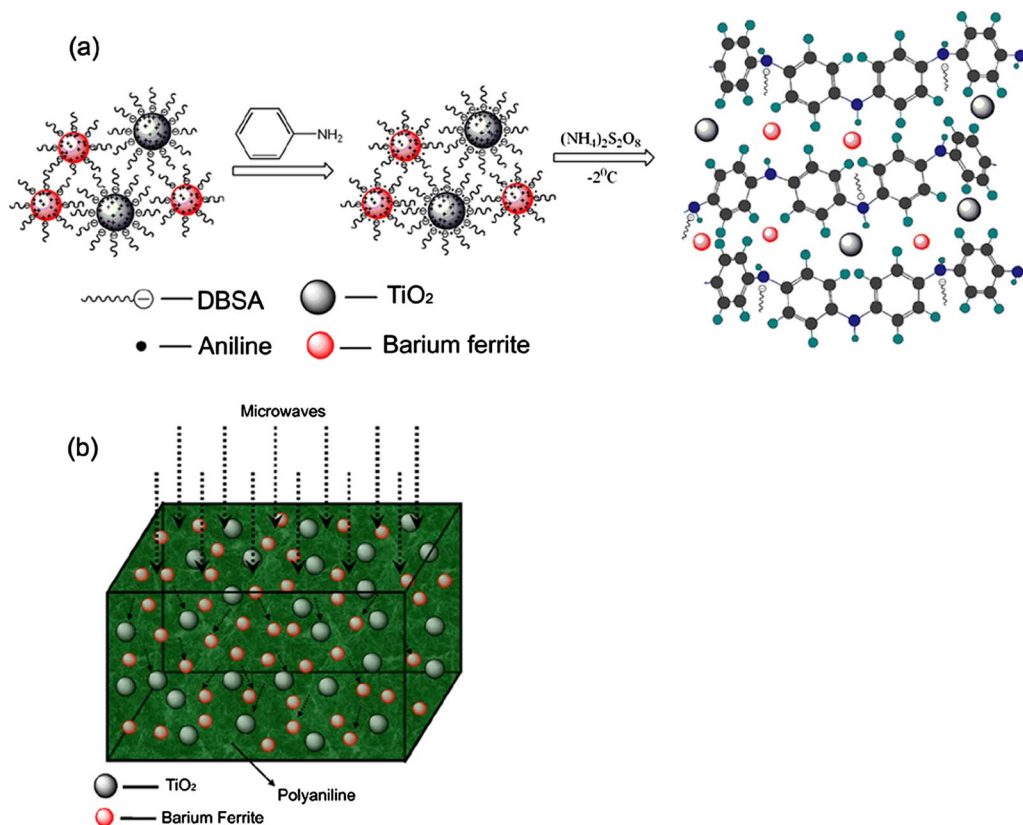

SCHEME 1. (Color online) Schematic representation of (a) polymerization of micellar solution of DBSA containing the barium ferrite and TiO₂ nanoparticles using ammonium persulphate (APS) as oxidant and (b) the interaction of the microwave with the polymer composite resulting in its attenuation due to the scattering with the nanoparticles.

added to the above solution and again homogenized for 2–3 h to form micelles of aniline with barium ferrite and TiO₂. The micelles so formed have been polymerized at 0 °C by emulsion polymerization using (NH₄)₂S₂O₈ (0.1M) as oxidant. The product so obtained has been demulsified by treating it with equal amount of isopropyl alcohol. The precipitate so obtained were filtered out and washed with alcohol and dried at 60–65 °C.

Different formulations of polymer composites have been synthesized in DBSA medium in order to check the effect of ferrite constituents on the properties. In these formulations aniline and TiO₂ weight ratio was kept constant and barium ferrite ratio was varied. In formulation PBT21, aniline and TiO₂ weight ratio is 1:1 and barium ferrite constituent is 0.5. Similarly, in PBT11 and PBT12 compositions, aniline to ferrite to TiO₂ weight ratios are in 1:1:1 and 1:2:1 proportions respectively. Beside this, polyaniline-TiO₂ (PT11) composite having monomer to TiO₂ weight ratio of 1:1, polyaniline-barium ferrite (PF12) with monomer to ferrite weight ratio of 1:2, and pure polyaniline doped with DBSA (PD13) have also been synthesized for comparative study.

The particle size and the morphology of TiO₂, barium ferrite, and polymer composites have been examined using transmission electron microscopy (TEM) (Phillips CM-12). The TEM samples have been prepared by dispersing the powder in isopropanol using sonification and placing small drop in the suspension on carbon coated copper grids. High resolution TEM (HRTEM) has been carried out on Technai G20-stwin (200 kV) with point resolution of 1.44 Å and line

resolution of 2.32 Å. The presence of TiO₂ and barium ferrite in the polymer composite has been confirmed by x-ray diffraction (XRD) studies carried out on D8 Advance x-ray diffractometer (Bruker) using Cu K α radiation ($\lambda = 1.540598$ Å) in scattering range (2θ) of 10°–70° with a scan rate of 0.02 deg/s and slit width of 0.1 mm. EM shielding and dielectric measurements have been carried out on an Agilent E8362B Vector network analyzer in the microwave range of 12.4–18 GHz (K_u -band). Powder samples have been compressed in the form of rectangular pellets (2 mm thick) and inserted in 15.8 × 7.9 × 6 mm³ copper sample holder connected between the waveguide flanges of network analyzer.

III. RESULTS AND DISCUSSION

Synthesis of polyaniline-TiO₂-barium ferrite is carried out using DBSA as surfactant which also work as a dopant. Due to the hydrophilic and hydrophobic parts in DBSA, it results in the formation of micelles and when this micellar solution is polymerize with the help of oxidant, polymerization takes place at the boundaries of the micelles and nanoparticles are trapped inside the polymer chain [Scheme 1(a)]. TEM and HRTEM images of the PBT nanocomposite are shown in Fig. 1. Figure 1(a) clearly shows that when the nanoparticles of TiO₂ and barium ferrite are polymerized along with aniline, they form a core-shell type of morphology. From the figure, it is also observed that an array of nanoparticles is formed during the *in situ* emulsion polymer-

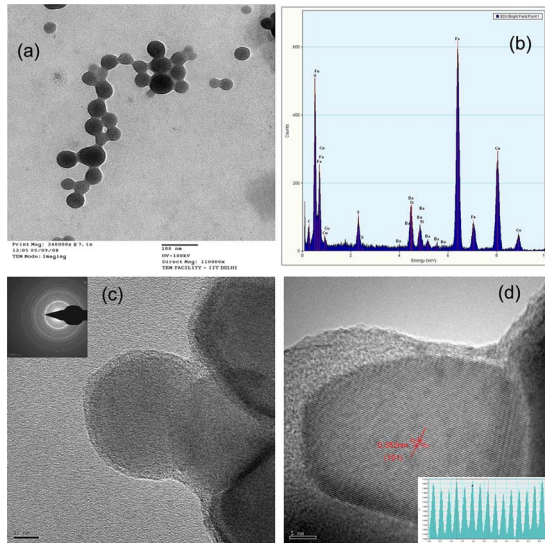


FIG. 1. (Color online) (a) Transmission electron micrograph of PBT12 nanocomposite showing the formation of array of nanoparticles via conducting matrix of polyaniline. (b) Energy dispersive x-ray pattern of PBT12 showing the approximate percentage of the element present in the nanocomposite. (c) HRTEM image of PBT21 while the inset demonstrates the electron diffraction pattern of PBT12 having ring of crystalline barium ferrite and TiO_2 . (d) HRTEM image, fringes indicate the presence of crystalline TiO_2 particle, while the outer shell shows the polymer matrix of PBT12 nanocomposite. The inset of (d) shows the depth profile of the fringe with d -spacing of 0.352 nm.

ization process and directly indicates that the particles are separated by the polymer matrix. The presence of conducting shell encapsulating the magnetic and dielectric nanoparticles is helpful in enhancing the absorption of the EM wave. HRTEM images of PBT21 [Fig. 1(c)] and PBT12 [Fig. 1(d)] also confirm the core-shell morphology of the nanocomposites. The shell of the particle gives an impression of an amorphous layer as no fringes have been observed at the shell while the d -spacing of the particles confirm the presence of TiO_2 nanoparticle at the core. The presence of other elements in the polymer composite is confirmed by the energy dispersive x-ray spectroscopy (EDAX) studies [Fig. 1(b)].

The presence of TiO_2 and barium ferrite in the nanocomposites is confirmed by XRD patterns [Fig. 2(a)]. The main peaks for TiO_2 are observed at 2θ values of 25.283° ($d=3.520$ Å), 37.784° ($d=2.379$ Å), 38.530° ($d=2.335$ Å), 48.032° ($d=1.893$ Å), 53.874° ($d=1.700$ Å), 55.025° ($d=1.667$ Å), and 62.660° ($d=1.481$ Å) corresponding to (101), (004), (112), (200), (105), (211), and (204) reflections [curve (a)], respectively. For barium ferrite, main peaks are observed at 2θ values of 30.294° ($d=2.9480$), 32.141° ($d=2.7827$), 34.083° ($d=2.6284$), 37.046° ($d=2.4247$), 40.254° ($d=2.2386$), 42.391° ($d=2.1305$), 55.018° ($d=1.6677$), 56.477° ($d=1.6280$), and 63.054° ($d=1.4731$) corresponding to the (110), (107), (114), (203), (205), (206), (217), (201), and (220) reflections [curve (f)], respectively. All the observed peaks have been matched with the standard XRD pattern of TiO_2 ¹⁷ and barium ferrite.¹⁸ The peaks of barium ferrite were observed in all the compositions of polyaniline composites with TiO_2 and barium ferrite, which indicates the presence of ferrite particles in the polymer matrix. The increase in the intensity of the peaks demonstrates

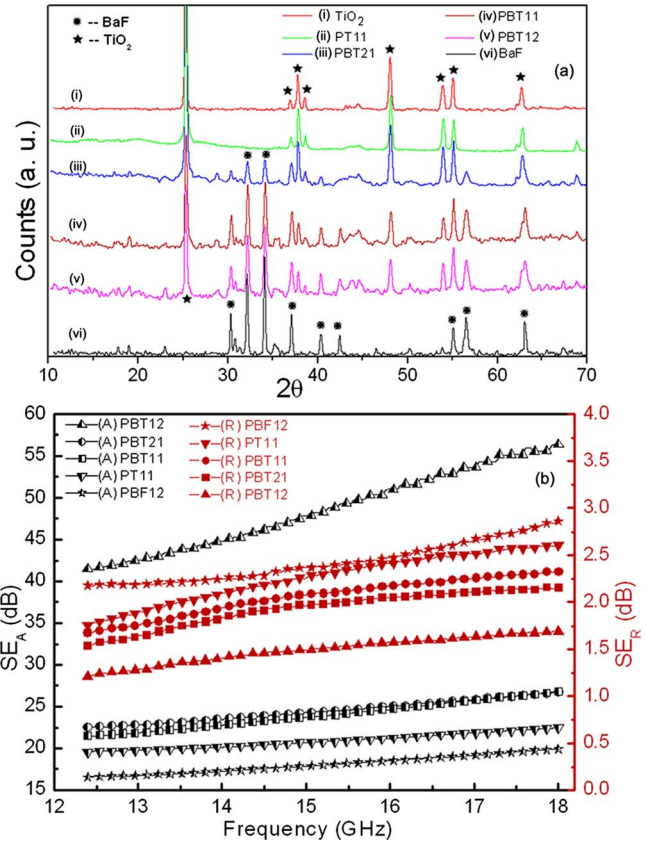


FIG. 2. (Color online) (a) XRD patterns of (i) TiO_2 , (ii) PT11, (iii) PBT21, (iv) PBT11, (v) PBT12, and (vi) Ba ferrite. Plots (c), (d), and (e) confirm the presence of TiO_2 and barium ferrite in the polymer composite. (b) Dependence of SE and SE_R on frequency showing the effect of barium ferrite concentration on the SE_A value of the nanocomposites.

the increase in the ratio of barium ferrite. The crystallite size of barium ferrite and TiO_2 has been calculated by using Scherrer's formula,

$$D = k\lambda / \beta \cos \theta, \quad (1)$$

where λ is the x-ray wavelength, k is the shape factor, D is the crystallite size for the individual peak of the crystal (in angstroms), θ is the Bragg angle (in degrees), and β is the full width at half maxima (in radians). The value of k is assigned as 0.89, which depends on several factors including the Miller index of the reflecting plane and the shape of the crystal. The crystallite size of barium ferrite particles has been calculated using Eq. (1) and estimated to be 25 nm, while the crystallite size of TiO_2 has been found to be 36.6 nm. The presence of peaks of TiO_2 and barium ferrite shows the formation of composite having separate phases of both the compounds dispersed in the polymer matrix.

The EMI SE of a material is defined as the ratio of transmitted power to the incident power and is given by

$$SE \text{ (dB)} = -10 \log \left(\frac{P_T}{P_O} \right), \quad (2)$$

where P_T and P_O are the transmitted and incident EM powers, respectively. For a shielding material, total $SE = SE_R + SE_A + SE_M$, where SE_R , SE_A , and SE_M are due to reflection, absorption, and multiple reflections, respectively.

In two port network, S -parameters $S_{11}(S_{22})$, $S_{21}(S_{12})$ represent the reflection and the transmission coefficients given as

$$T = \left| \frac{E_T}{E_I} \right|^2 = |S_{21}|^2 = |S_{12}|^2, \quad (3)$$

$$R = \left| \frac{E_R}{E_I} \right|^2 = |S_{11}|^2 = |S_{22}|^2, \quad (4)$$

and

$$\text{absorption coefficient } (A) = 1 - R - T. \quad (5)$$

Here, it is noted that the absorption coefficient is given with respect to the power of the incident EM wave. If the effect of multiple reflections between both interfaces of the material is negligible, then the relative intensity of the effective incident EM wave inside the material after reflection is based on the quantity $(1-R)$. Therefore, the effective absorbance (A_{eff}) can be described as $A_{\text{eff}} = (1-R-T)/(1-R)$ with respect to the power of the effective incident EM wave inside the shielding material. It is convenient to express the reflectance and effective absorbance in the form of $-10 \log(1-R)$ and $-10 \log(1-A_{\text{eff}})$ in decibel (dB), respectively,¹⁹ which give SE_R and SE_A as

$$SE_R = -10 \log(1-R) \quad (6)$$

and

$$SE_A = -10 \log(1-A_{\text{eff}}) = -10 \log \frac{T}{1-R}. \quad (7)$$

For the material the skin depth (δ) is the distance up to which the intensity of the EM wave decrease to $1/e$ of its original strength. The skin depth is related with the attenuation constant (β) of the wave propagation vector $\delta = 1/\beta = \sqrt{2/\omega\mu\sigma_{\text{ac}}}$ with the approximations that $\sigma \gg \omega\epsilon$. As $\delta \propto \omega^{-1/2}$, therefore, at low frequencies for the electrically thin samples ($d \ll \delta$) the SE of the sample is describe as

$$SE \text{ (dB)} = 20 \log\left(1 + \frac{1}{2}Z_0 d \sigma\right), \quad (8)$$

where σ is the ac conductivity, Z_0 is free space impedance, and d is the sample thickness. While for the higher frequencies, sample thickness (electrically thick samples) is sufficiently greater than skin depth and EMI SE for the plane electromagnetic wave²⁰ is given as

$$SE \text{ (dB)} = SE_R \text{ (dB)} + SE_A \text{ (dB)}, \quad (9)$$

$$SE_R \text{ (dB)} \approx 10 \log\left(\frac{\sigma_{\text{ac}}}{16\omega\epsilon_0\mu_r}\right), \quad (10)$$

and

$$SE_A \text{ (dB)} = 20 \frac{d}{\delta} \log e, \quad (11)$$

where σ_{ac} depends on the dielectric properties²¹ ($\sigma_{\text{ac}} = \omega\epsilon_0\epsilon''$) of the material, ω is the angular frequency ($\omega = 2\pi f$), ϵ_0 is the free space permittivity, and μ_r is the relative magnetic permeability of the sample. In Eq. (9), the first term is related to the reflection of the EM wave and contributes as

the SE due to reflection. The second term expresses the loss due to the absorption of the wave when it passes through the shielding material. In microwave range, the contribution of the second part becomes more as compared to the reflection term.

In metallic materials, the SE is very high and mainly attributed to the reflection of the EM radiation due to its high conductivity, whereas in the case of conducting polymers having moderate conductivity the contribution to the SE comes from both the reflection and the absorption. It has been observed that conducting ferromagnetic composites of polyaniline with barium ferrite and TiO_2 have SE mainly due to absorption. Figure 2(b) shows the variation in the SE with frequency in the 12.4–18 GHz range. As seen in the figure, PBF12 shows the SE_A value of 19 dB, while for PT11 nanocomposite, the SE_A value of 22 dB is observed. With the addition of barium ferrite nanoparticles in the ratios of 2:1 and 1:1, an increase in the microwave absorption is nominal (~ 3 dB), but when double amount of barium ferrite is taken as compared to TiO_2 (sample PBT12), substantial enhancement in the absorption of EM radiation is observed. The maximum SE of 58 dB has been achieved for the PBT12 sample having the polymer: TiO_2 :ferrite ratio of 1:1:2. It is observed that the SE increases with the increase in the ferrite concentration and with the increase in frequency. The increase in the absorption part is mainly attributed to the presence of a high dielectric constant material and a magnetic material which increase more scattering, which, in turn, results in more attenuation of the EM radiations [Scheme 1(b)].

To investigate the possible mechanism and effects giving rise to the improvement in microwave absorption, complex permittivity ($\epsilon_r = \epsilon' - j\epsilon''$), and permeability ($\mu_r = \mu' - j\mu''$) of the samples were measured. The real (ϵ') and imaginary (ϵ'') parts of complex permittivity versus frequency are shown in Figs. 3(a) and 3(b). The real part (ϵ') is mainly associated with the amount of polarization occurring in the material and the imaginary part (ϵ'') is related to the dissipation of energy. In polyaniline, strong polarization occurs due to the presence of polaron/bipolaron and other bound charges which leads to high value of ϵ' and ϵ'' . With the increase in frequency, the dipoles present in the system cannot reorient themselves along with the applied electric field, as a result of which dielectric constant decreases. The main characteristic feature of TiO_2 is that it has high dielectric constant with dominant dipolar polarization and the associated relaxation phenomenon constitutes the loss mechanism.²² With the addition of barium ferrite and TiO_2 in polyaniline matrix, significant increase in the imaginary part of complex permittivity has been observed. The higher values of the dielectric loss is attributed to the more interfacial polarization due to the presence of insulating barium ferrite particles and high dielectric TiO_2 particles which consequently lead to more SE due to absorption.

Figures 3(c) and 3(d) show the variation in the real part and imaginary part of magnetic permeability with frequency. The magnetic permeability of all the samples decreases with the increase in frequency, whereas higher magnetic loss has been observed for higher percentage of barium ferrite

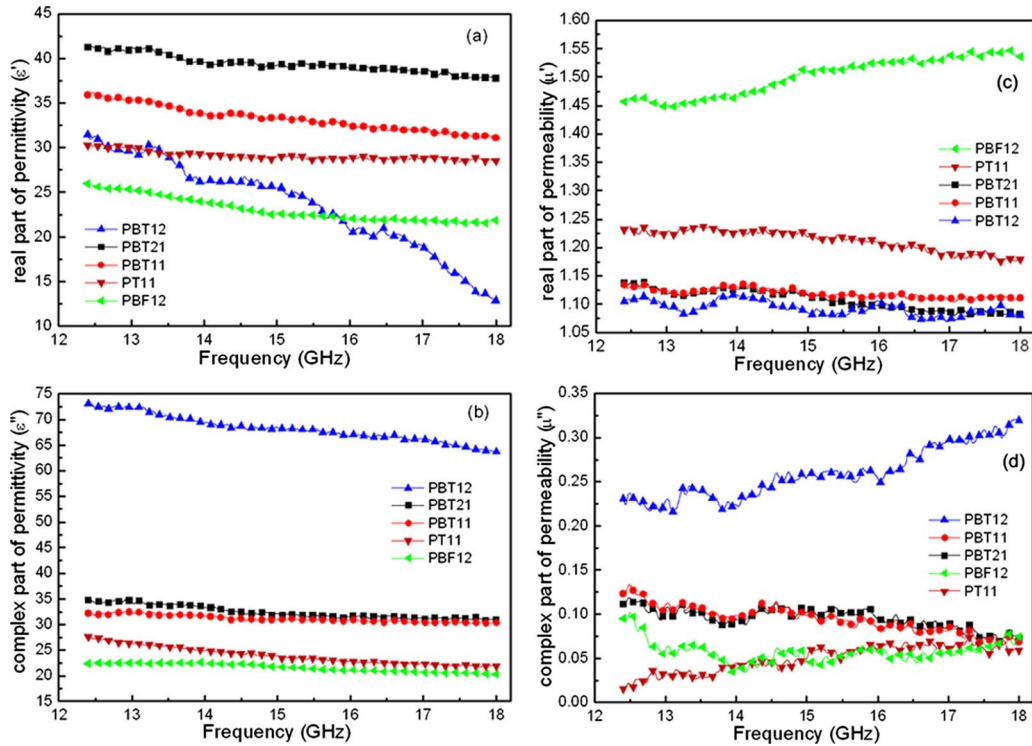


FIG. 3. (Color online) (a) Behavior of (a) real and (b) imaginary parts of permittivity. (c) and (d) show the variation in real and imaginary parts of magnetic permeability with the change in frequency for the samples PBT12 (▲), PBT11 (●), PBT21 (■), PBF12 (◄), and PT11 (▼)

(PBT12) in the polymer matrix. The magnetic loss is caused by the time lag of magnetization vector (M) behind the magnetic field vector. The change in magnetization vector is generally brought about by the rotation of magnetization and the domain wall displacement. These motions lag behind the change in the magnetic field and contribute to the magnetic loss (μ''). The rotation of the domain of magnetic nanoparticles might become difficult due to the effective anisotropy (magnetocrystalline anisotropy and shape anisotropy). The surface area, number of atoms with dangling bonds, and unsaturated coordination on the surface of polymer matrix are all enhanced. These variations lead to the interface polarization and multiple scattering, which is useful for the absorption of large number of microwaves.²³

Figure 4(a) (inset) shows the variation in σ_{ac} with the frequency for the sample PBT11, calculated from the dielectric measurements ($\sigma_{ac} = \omega \epsilon_0 \epsilon''$). To relate σ_{ac} to the shielding parameters of the material, SE_R is plotted against $\log \sigma_{ac}$ [Fig. 4(a)]. Higher value of conductivity is required for high SE due to reflection. For the absorption part, the skin depth of the samples has been calculated using the relation, $\delta = \sqrt{2/\omega\mu\sigma_{ac}}$ and its variation with frequency is shown in Fig. 4(b) (inset). It has been observed that the skin depth decreases with frequency, which demonstrates that mainly surface conduction exists at the higher frequencies. The dependence of skin depth on the conductivity and magnetic permeability reveal that for highly conducting and magnetic material, the skin depth is very small. From Eq. (11), better SE_A can be achieved from the highly conducting and magnetic materials. The dependence of SE_A on $(\sigma_{ac})^{1/2}$ is shown in Fig. 4(b).

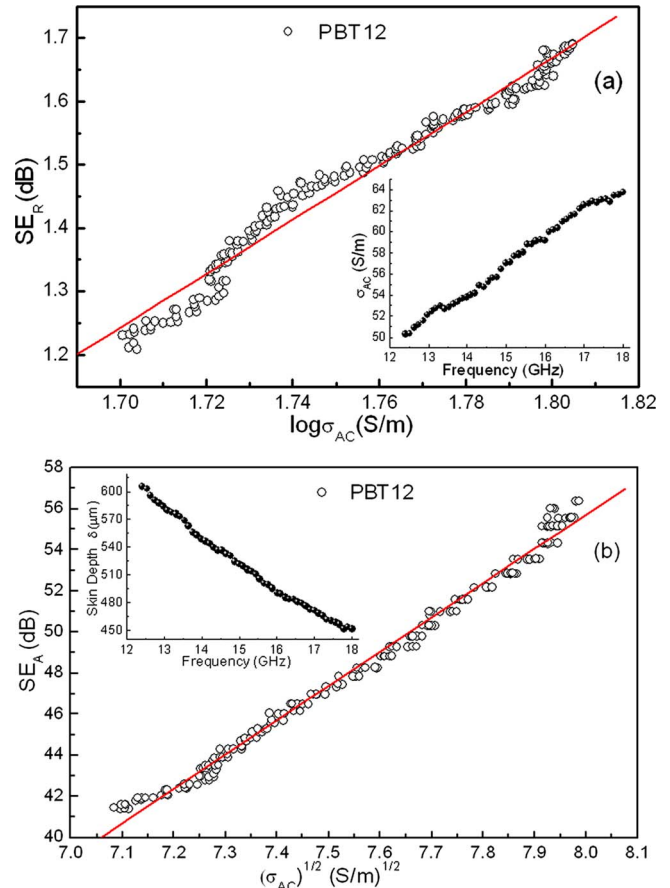


FIG. 4. (Color online) (a) Variation in SE_R as a function of $\log \sigma_{ac}$, while the inset shows the variation in σ_{ac} with the increase in frequency. (b) Variation in SE_A as a function of $(\sigma_{ac})^{1/2}$, while the inset shows the change in skin depth (δ) with the increase in frequency for the PBT12 sample.

IV. CONCLUSIONS

In conclusion, polyaniline-TiO₂-barium ferrite nanocomposites, prepared by the microemulsion method, have excellent microwave absorption properties. The microwave absorption property of the composites strongly depends on the intrinsic properties of barium ferrite and TiO₂ nanoparticles in the polymer matrix. The incorporation of TiO₂ and barium ferrite results in the formation of array of nanoparticles, which leads to more interfacial dipolar polarization and higher anisotropic energy due to the nanosize that consequently contributes to the high values of SE due to absorption. The dependence of SE_A on the magnetic permeability and ac conductivity shows that better absorption value has been obtained for material with higher conductivity and magnetization.

ACKNOWLEDGMENTS

The authors wish to thank Director N.P.L for his keen interest in the work. The authors also thank Dr. Rashmi for recording XRD pattern of the samples. A.O. is thankful to CSIR for providing the necessary fellowship.

¹Y. K. Hong, C. Y. Lee, C. K. Jeong, D. E. Lee, K. Kim, and J. Joo, *Rev. Sci. Instrum.* **74**, 1098 (2003).

²H. K. Kim, M. S. Kim, K. Song, Y. H. Park, S. H. Kim, J. Joo, and J. Y. Lee, *Synth. Met.* **135**, 105 (2003).

³N. H. Hoang, J. L. Wojkiewicz, J. L. Miane, and R. S. Biscarro, *Polym.*

Adv. Technol. **18**, 257 (2007).

⁴Y. Wang and X. Jing, *Polym. Adv. Technol.* **16**, 344 (2005).

⁵S. K. Dhawan, N. Singh, and S. Venkatachalam, *Synth. Met.* **129**, 261 (2002).

⁶N. C. Das, S. Yamazaki, M. Hikosaka, T. K. Chaki, D. Khastgir, and A. Chakraborty, *Polym. Int.* **54**, 256 (2005).

⁷H. M. Kim, K. Kim, C. Y. Lee, J. Joo, S. J. Cho, H. S. Yoon, D. A. Pejakovic, J. W. Yoo, and A. J. Epstein, *Appl. Phys. Lett.* **84**, 589 (2004).

⁸Y. Huang, N. Li, Y. Ma, F. Du, F. Li, X. He, X. Lin, H. Gao, and Y. Chen, *Carbon* **45**, 1614 (2007).

⁹K. Y. Park, S. E. Lee, C. G. Kim, and J. H. Han, *Compos. Struct.* **81**, 401 (2007).

¹⁰P. Chandrasekhar and K. Naishadham, *Synth. Met.* **105**, 115 (1999).

¹¹J. L. Wallace, *IEEE Trans. Magn.* **29**, 4209 (1993).

¹²B. W. Li, Y. Shen, Z. X. Yue, and C. W. Nan, *J. Magn. Magn. Mater.* **313**, 322 (2007).

¹³J. R. Liu, M. Itoh, and K. Machida, *Appl. Phys. Lett.* **83**, 4017 (2003).

¹⁴R. Che, L. M. Peng, X. Duan, Q. Chen, and X. Liang, *Adv. Mater. (Weinheim, Ger.)* **16**, 401 (2004).

¹⁵S. M. Abbas, R. Chatterjee, A. K. Dixit, A. V. R. Kumar, and T. C. Goel, *J. Appl. Phys.* **101**, 074105 (2007).

¹⁶J. Qiu, H. Shen, and M. Gu, *Powder Technol.* **154**, 116 (2005).

¹⁷JCPDS Card No. 84-1285.

¹⁸JCPDS Card No. 39-1433.

¹⁹K. Singh, A. Ohlan, P. Saini, and S. K. Dhawan, *Polym. Adv. Technol.* **19**, 229 (2008).

²⁰N. F. Colaneri and L. W. Shacklette, *IEEE Trans. Instrum. Meas.* **41**, 291 (1992).

²¹R. Singh, J. Kumar, R. K. Singh, R. C. Rastogi, and V. Kumar, *New J. Phys.* **9**, 40 (2007).

²²D. L. Leslie-Pelecky and R. D. Rieke, *Chem. Mater.* **8**, 1770 (1996).

²³X. F. Zhang, X. L. Dong, H. Huang, Y. Y. Liu, W. N. Wang, X. G. Zhu, B. Lv, J. P. Lei, and C. G. Lee, *Appl. Phys. Lett.* **89**, 053115 (2006).